

Fractional-flux Little-Parks resistance oscillations in disordered superconducting $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders

YU. ZADOROZHNY and Y. LIU

Department of Physics, The Pennsylvania State University - University Park, PA 16802, U.S.A.

PACS. 74.40.+k – Fluctuations (noise, chaos, nonequilibrium superconductivity, localization, etc.).

PACS. 74.50.+r – Proximity effects, weak links, tunneling phenomena, and Josephson effects.

PACS. 74.76.Db – Conventional superconducting films.

Abstract. – Resistance of disordered superconducting $\text{Au}_{0.7}\text{In}_{0.3}$ cylindrical films was measured as a function of applied magnetic field. In the high-temperature part of the superconducting transition regime, the resistance oscillated with a period of $h/2e$ in the unit of the enclosed magnetic flux. However, at lower temperatures, the resistance peaks split. We argue that this splitting is due to the emergence of an oscillation with a period of $h/4e$, half of the flux quantum for paired electrons. The possible physical origin of the $h/4e$ resistance oscillation is discussed in the context of new minima in the free energy of a disordered superconducting cylinder.

The essence of superconductivity lies in the long-range phase coherence, which is manifested, in particular, in the Little-Parks (L-P) resistance oscillation [1]. Strong disorder, magnetic field, or Coulomb interaction suppresses this long-range phase coherence, leading in two dimensions (2D) to the superconductor-to-insulator (S-I) transition [2]. Several intriguing physical pictures have emerged from the study of systems in the vicinity of the 2D S-I transition. For example, in disordered 2D films, Cooper pairs may form but do not condense into a superconducting state. These Cooper pairs then behave as (charged) point bosons [3]. Alternatively, Cooper pairs in disordered superconducting samples can become so fragile that their non-bosonic nature is manifested, leading, surprisingly, to negative Josephson coupling constants [4]. Interestingly, a resistance oscillation with a novel period, $h/4e$, half of the conventional flux quantum $\Phi_0 = h/2e$, emerges in these studies [4, 5].

Fractional-flux resistance oscillation (with a period of $h/2e$ rather than h/e) due to coherent back scattering of unpaired electrons have been observed in disordered *normal-metal* cylinders [6]. Even though the L-P resistance oscillation observed in superconducting cylinders [1] has the same period, $h/2e$, the flux quantum for Cooper pairs, the physical origin of the L-P effect is very different [7]. The free energy of a superconducting cylinder is a periodic function of the enclosed magnetic flux, resulting in an oscillation in the superconducting critical temperature (T_c) and in the sample resistance. While superconducting rings [8–10] and cylinders [11] have been studied in recent years, the effect of disorder on the L-P resistance oscillation has never been examined systematically. We have carried out experimental studies

of disordered superconducting Au-In cylinders to search for oscillations with novel periods. Here we present experimental results obtained on $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders for which both $h/2e$ and $h/4e$ resistance oscillations have been observed.

To prepare a sample, a fine filament was drawn from a quartz melt and placed across a gap in a thin glass slide. The slide was then attached to a rotator inside a high-vacuum evaporation system. A cylindrical film of $\text{Au}_{0.7}\text{In}_{0.3}$ was prepared by sequential deposition of 99.9999% pure Au and In (Au, In, Au, In, and Au in the appropriate proportion) onto the rotating filament. Depth profiles obtained by X-ray photoelectron spectroscopy (XPS) and ion etching showed [12] that thin alternating layers of Au and In completely inter-diffused even at room temperature, as was also found previously [13]. We also found that Au-In alloy adhered well to quartz without significant oxidation, forming high quality, uniform films. Even the thinnest $\text{Au}_{0.7}\text{In}_{0.3}$ films made, a 20 nm thick cylindrical film and an 8 nm thick planar film, exhibited low normal-state resistivity and were superconducting. In contrast, pure In cylinders studied in the past [14], as well as in our own control experiments, were not superconducting unless a much thicker film (≈ 300 nm) was used. After the deposition, the cylinder was transferred to an alumina substrate. Several fine Au wires were attached to the cylinder using Ag epoxy, which also anchored the cylinder to the substrate.

Electrical transport measurements were carried out in a dilution refrigerator equipped with a superconducting magnet. The cylinders were manually aligned parallel to the magnetic field. Radio-frequency filters with insertion losses of 10 dB at 10 MHz and 50 dB at 300 MHz were used on all electrical leads entering the sample enclosure. The sample resistance was measured in d.c. using a Keithley 220 current source and a Keithley 182 nanovoltmeter. Control measurements using a manually operated battery powered d.c. current source and also by a.c. lock-in technique yielded identical results. The resistance data presented here were obtained using a bias current of 100 nA. The reported resistance oscillations were verified to be bias-independent throughout the Ohmic I-V regime, down to 100 pA bias current.

In Fig. 1, values of normalized resistance are plotted against temperature for two samples, Cylinders 38-5 and 43-3. For Cylinder 38-5, the diameter $d = 820$ nm, wall thickness $t = 35$ nm, length $l = 0.44$ mm, and normal state resistance $R_N = 1226 \Omega$ ($R_N^\square = 7.2 \Omega$). For Cylinder 43-3, $d = 470$ nm, $t = 30$ nm, $l = 0.37$ mm, and $R_N = 2248 \Omega$ ($R_N^\square = 9.0 \Omega$). The characteristic low-temperature tail in $R(T)$ was found in most of the samples and was therefore attributed to the intrinsic properties of the material. The onset temperature for the $h/4e$ resistance oscillation (see below) was typically above that of the tail. We therefore conclude that the $h/4e$ oscillation was not directly related to the presence of the tail. We studied the film structure throughout the entire length of several samples using a scanning electron microscope (SEM) as well as an atomic force microscope (AFM) and confirmed that the cylinders were granular and uniform on length scales beyond the grain size (≈ 30 nm). The inset of Fig. 1 contains pictures of a section of Cylinder 43-3 taken by SEM (large scale) and by AFM (smaller scale).

Fig. 2 shows normalized resistances of the two cylinders measured as a function of magnetic field at various temperatures. At higher temperatures, the resistance oscillates with a single period, $\Delta H = 40$ G and 125 G for Cylinders 38-5 and 43-3 respectively, which corresponds to an $h/2e$ oscillation. Below certain temperature thresholds, 0.315 K for Cylinder 38-5 and 0.320 K for Cylinder 43-3, the oscillation peaks split as additional resistance minima develop between the minima of the $h/2e$ oscillation. As the temperature is lowered, the depth of these secondary minima grows and becomes comparable to that of the primary ones. This trend is also seen as the magnetic field is increased, with secondary minima increasing in width and depth until the oscillation decays in higher fields. Similar features in resistance oscillations were found in all but a few of more than 40 samples studied. However, control samples of pure

In (capped with a very thin layer of Au to avoid oxidation) prepared under similar conditions did not show any splitting of the oscillation peaks.

Can the observed splitting of the oscillation peaks be explained based on the sample geometry? For example, a splitting may result from coexisting oscillations of two slightly different periods. This could be possible if the sample consisted of two sections of distinct diameters. However, a systematic examination of our data rules out this possibility. If the splitting of resistance peaks were indeed due to the presence of sections of different diameters, we would expect to see the peaks split into three or more in different samples or in the same sample at different temperatures. Experimentally, the oscillation peaks always split into two. In addition, extensive AFM studies did not reveal any large-scale inhomogeneities or identifiable segments of distinct diameters.

An alternative scenario is that the film might somehow consist of two co-axial superconducting shells. Below we show that this can also be excluded from being the origin of the splitting. First, as pointed out above, sequentially evaporated Au and In completely inter-diffuse. Therefore our samples do not consist of two coaxial cylindrical shells. Second, even the interdiffusion were somehow incomplete, resulting in a two-shells structure, the two shells would be coupled by proximity effect and would behave as a single cylinder. Our cylinders were 30nm or 35nm thick. The two shells would be separated by about 10nm. However, the zero-temperature coherence length for $\text{Au}_{0.7}\text{In}_{0.3}$ is 300-400nm (determined from the upper critical field measurements), which is much larger than the shell separation even if they did exist. Finally, the two-shell scenario is inconsistent with results obtained from other samples. Cylinders grown in a Au/In/Au sequence also showed a similar, but weaker splitting [15]. For these samples there is no physical basis for a two-shell scenario. In addition, the splitting for some cylinders (data not shown) were found to be quite large. To account for the large splitting, the separation of the two shells would have to exceed the film thickness, which is not possible.

The splitting of the resistance peaks can be understood if we track the positions of the resistance minima, rather than maxima. The primary minima occur at magnetic field values corresponding to integer numbers of magnetic flux quanta enclosed in the cylinder. The positions of the secondary minima, on the other hand, are given by half-integer numbers of flux quanta. The secondary minima can then be interpreted as a half-flux, $h/4e$, resistance oscillation coexisting with the conventional $h/2e$ oscillation. It should be emphasized that the coexistence of the $h/2e$ and $h/4e$ resistance oscillations does not necessarily imply a simple addition of two periodic functions (see below for more discussion).

A Fourier analysis of the data was carried out. Displayed in Fig. 3 are Fourier power spectra of some of the $R(H)$ curves shown in Fig. 2. The higher temperature spectra contain only a strong peak around the frequency corresponding to the $h/2e$ period. At lower temperatures, however, a peak corresponding to an $h/4e$ oscillation develops and eventually becomes comparable in magnitude to that of the $h/2e$ oscillation, supporting the conclusion drawn from analyzing the $R(H)$ data.

It has been proposed that conduction paths encircling a multi-connected sample twice without crossing themselves would lead to an $h/4e$ resistance oscillation [16]. However, since $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders are structurally uniform and highly conducting even in the normal state, it is unlikely that such non-crossing paths can exist in the sample. An interesting question is whether the observed $h/4e$ resistance oscillation is indeed a consequence of the coherent back scattering of Cooper pairs as proposed in Ref. [5]. While such possibility can not be excluded, no detailed theory of weak localization of Cooper pairs has been worked out [17], making it difficult to draw a conclusion on our results in this context.

Splitting of the $h/2e$ oscillation peaks was previously observed for a mesoscopic normal-

metal (Ag) ring bordered by two superconducting (Al) islands [18]. Normal electrons or holes undergo Andreev reflection at the normal-metal-superconductor (NS) interfaces and pick up the phase of the superconducting order parameter. The splitting was believed to result from the ring's conductance being a periodic function of the phase difference between the two superconductors with a period of π . Subsequently, better controlled experiments in similar geometry demonstrated a 2π periodicity [19], as expected [20]. An explanation for the result of [18] is in fact still lacking. As we argue below, the physics involved in our samples is different from that in NS heterostructures.

Splitting was also found in the first oscillation peak for mesoscopic Al rings [8]. This splitting, however, was associated with the presence of the so-called resistance anomaly, a resistance peak in $R(T)$ just below the T_c . The anomaly results from charge imbalance near an NS interface [8]. No such resistance anomaly was observed in our $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders. Therefore we believe that the splitting in Al loops is unrelated to our observations.

Physically, it might be reasonable to expect that the fractional-flux resistance oscillation can be understood on the same footing as the conventional L-P effect. Within the Ginzburg-Landau theory, the phase boundary between the superconducting and the normal phases, $T_c(H)$, obtained by tracking a fixed resistance value on the $R(H, T)$ surface, reflects the landscape of the free energy in the H - T space [7]. For pure samples, for which $R(T)$ shifts rigidly as the magnetic field is swept [14], any resistance value can be chosen for this purpose, as long as it is reasonably below R_N .

We have studied in detail the evolution of the cylinder resistance as a function of H and T , as shown in Fig. 4 for Cylinder 43-3. It is evident from Fig. 4 that the fractional-flux resistance oscillation persists to the lowest temperatures at which a non-zero resistance is still observable. In addition, as has been mentioned, the $h/4e$ oscillation is bias-independent for at least three decades of bias current. These observations suggest that the fractional periodicity is an equilibrium property of the global superconducting state.

By analogy with the standard approach, we have obtained two "phase boundaries" by tracking fixed resistance values of $R = 250 \, \Omega$ and $50 \, \Omega$. While the former curve resembles the phase boundary of a pure superconducting cylinder, the one at $50 \, \Omega$ shows splitting of the oscillation peaks (Fig. 4). The $T_c(H)$ curve corresponding to $R = 50 \, \Omega$, being lower in temperature, should be closer to the landscape of the free energy of the superconducting state of the sample. Therefore, the presence of the secondary resistance minima is an indication that the free energy of $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders develops additional minima at half-integer numbers of flux quanta.

In the free energy consideration, it is natural to analyze the oscillation based on the positions of the energy minima rather than maxima. Furthermore, the free energy oscillations of $h/2e$ and $h/4e$ periods are not simply added together, but rather the lowest energy state is chosen at each value of the magnetic field. This explains why no new features appeared at the primary resistance minima as the secondary minima developed. It has been shown, based on microscopic consideration, that the free energy of a non-disordered superconducting cylinder is minimized for integer numbers of flux quanta [21]. The same is true for a ring or cylinder with (conventional) Josephson junctions embedded along the circumference.

However, the situation is different for samples containing junctions with negative instead of positive Josephson coupling, known as π -junctions [22]. The free energy of a superconducting ring interrupted by such a junction has a minimum at $\Phi_0/2 = h/4e$ [22]. Since the free energy has to be a periodic function of the enclosed flux [21], this means that free energy minima occur at all half-integer numbers of flux quanta. This result can be generalized to a ring containing an odd number of π -junctions [23]. (The free energy of a ring with an even number of π -junctions has minima at integer numbers of flux quanta, as usual.) The free energy of a

superconducting cylinder, which can be considered as a collection of rings, should have minima at both integer- and half-integer flux quanta if there are odd numbers of π -junctions in some of the rings.

The above picture relies on the presence of Josephson junctions in our cylinders. For Au-In alloy, the maximum solid solubility of In in Au is about 10% [26]. In a $\text{Au}_{0.7}\text{In}_{0.3}$ film, In-rich regions of varying size are expected to form in a uniform $\text{Au}_{0.9}\text{In}_{0.1}$ matrix as the excess In precipitates. Such phase separation has been confirmed by XPS studies of planar $\text{Au}_{0.7}\text{In}_{0.3}$ films [12] and appears to occur in cylindrical films as well. The characteristic length scale on which the In concentration varies is given by the average grain size. At low temperatures, superconducting In-rich regions are linked by Josephson coupling, forming a random superconductor-normal metal-superconductor (SNS) junction array.

Negative Josephson coupling in these SNS Josephson junctions may emerge from mesoscopic fluctuations in disordered superconductors, as proposed originally by Spivak and Kivelson [4] for films close to the S-I transition in zero magnetic field. Zhou and Spivak [24] have analyzed disordered superconducting films in a parallel field, a case applicable to our system. In particular, the Josephson coupling between two superconducting droplets embedded in a normal metal in parallel magnetic field, and its fluctuation, have been calculated explicitly [25]. As the magnetic field increases, the average coupling vanishes while the fluctuation in the coupling remains essentially unchanged. This is only possible if both positive and negative couplings are allowed. Otherwise, the fluctuation would have to go to zero along with the average. Therefore, the pi-junction becomes more favored as the field increases, leading to an increase in the part of free energy that possesses minima at half-integer flux quanta. This will in turn enhance the $h/4e$ resistance oscillation, which may account for the observed increase in the $h/4e$ oscillation component in higher fields.

In conclusion, we have observed a splitting of peaks in the resistance oscillation in $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders close to the bottom of the superconducting transition. We have argued that this is due to the emergence of a resistance oscillation of period $h/4e$. We have examined this oscillation in the context of the presence of new minima in the free energy of the cylinders at half-integer numbers of flux quanta. More theoretical work is needed to clarify the physical origin of the observed $h/4e$ resistance oscillation.

* * *

The authors would like to acknowledge useful discussion with A. M. Goldman, J. K. Jain, S. Kivelson, M. Ma, and F. Zhou. They would also like to acknowledge valuable contributions of David Herman and Karl Nelson to this project. This work is supported by the NSF under grant DMR-9702661.

REFERENCES

- [1] LITTLE W. A. and PARKS R. D., *Phys. Rev. Lett.*, **9** (1962) 9
- [2] See, for example, MARKOVIC N. and GOLDMAN A. M., *Phys. Today*, **51** (11) (1998) 39, and references cited therein.
- [3] FISHER M. P. A., *Phys. Rev. Lett.*, **65** (1990) 923
- [4] KIVELSON S. A. and SPIVAK B. Z., *Phys. Rev. B*, **43** (1991) 3740 **45** (1992) 10490
- [5] DE VEGVAR P. G. N. and GLAZMAN L., *Phys. Rev. Lett.*, **71** (1993) 2351
- [6] ARONOV A. G. and SHARVIN YU. V., *Rev. Mod. Phys.*, **59** (1987) 755
- [7] TINKHAM M., *Introduction to Superconductivity* (McGraw Hill, New York) 1996, p. 128.
- [8] VLOEBERGHES H. *et al.*, *Phys. Rev. Lett.*, **69** (1992) 1268

- [9] ZHANG X. and PRICE J. C., *Phys. Rev. B*, **55** (1997) 3128
- [10] DAVIDOVIC D. *et al.*, *Phys. Rev. B*, **55** (1997) 6518
- [11] GORDON J. M., *Phys. Rev. B*, **30** (1984) 6770
- [12] NameZadorozhny Yu. and Liu Y. preprint, cond-mat/0011522 (2000)
- [13] SIMIĆ V. and MARINKOVIĆ Ž., *Thin Solid Films*, **41** (1977) 57
- [14] MEYERS L. and MESERVEY R., *Phys. Rev. B*, **4** (1971) 824
- [15] ZADOROZHNY YU., HERMAN D. R., and LIU Y., *Phys. Rev. B*, **63** (2001) 144521
- [16] SÁ DE MELO C. A. R., *Phys. Rev. B*, **53** (1996) 6010
- [17] WEICHMAN P. B., *Recent Progress in Many-Body Theories*, edited by T. L. AINSWORTH *et al.*, Vol. **3** (Plenum Press, New York) 1992, p. 361.
- [18] PETRASHOV V. T. *et al.*, *Phys. Rev. Lett.*, **70** (1993) 347
- [19] For a review, see LAMBERT C. J. and RAIMONDI R., *J. Phys.: Condens. Matter*, **10** (1998) 901
- [20] ZHOU F. and SPIVAK B., *JETP Lett.*, **65** (1997) 369
- [21] BYERS N. and YANG C. N., *Phys. Rev. Lett.*, **7** (1961) 46
- [22] BULAEVSKII L. N., KUZII V. V., and SOBYANIN A. A., *JETP Lett.*, **25** (1977) 290
- [23] ZHOU F., personal communications
- [24] ZHOU F. and SPIVAK B. Z., *Phys. Rev. Lett.*, **80** (1998) 5647
- [25] ZHOU F., *Int. J. Mod. Phys. B*, **13** (1999) 2229
- [26] OKAMOTO H. and MASSALSKI T. B. (Editors), *Phase Diagrams of Binary Gold Alloys* (ASM International, Material Park, Ohio) 1987, p. 142

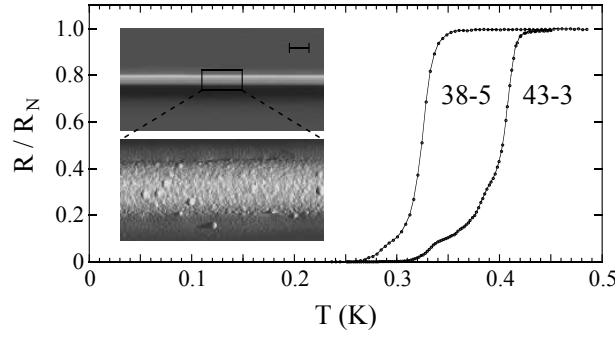


Fig. 1 – Normalized resistances of two $\text{Au}_{0.7}\text{In}_{0.3}$ cylinders plotted as a function of temperature in zero applied magnetic field. The insets are SEM (top) and AFM (bottom) pictures of Cylinder 43-3, capped by 5nm of Au to facilitate imaging. The scale bar is $1\ \mu\text{m}$ long. The bottom picture is $2 \times 1\ \mu\text{m}^2$.

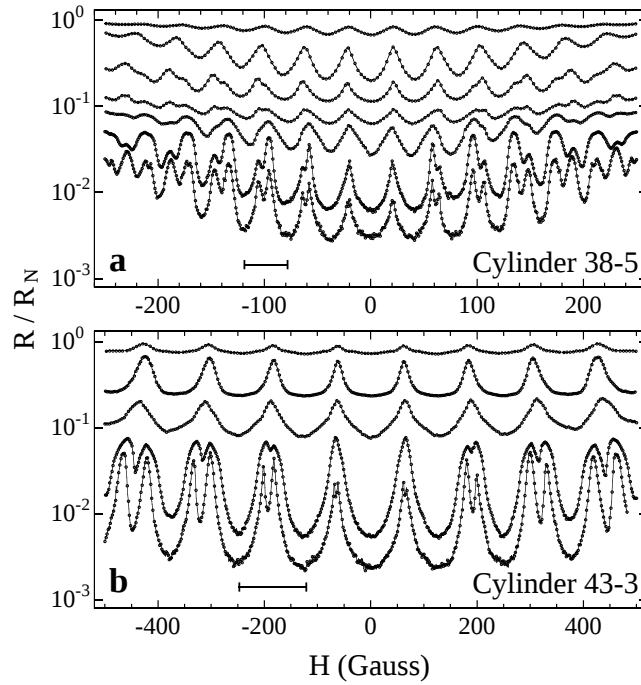


Fig. 2 – Normalized resistance of Cylinders 38-5 (**a**) and 43-3 (**b**) plotted as a function of parallel magnetic field at fixed temperatures. From top to bottom $T = 0.33, 0.315, 0.31, 0.297, 0.29, 0.28,$ and $0.27\ \text{K}$ for **a** and $0.39, 0.36, 0.33, 0.31,$ and $0.30\ \text{K}$ for **b**. The bars indicating the oscillation periods are $40\ \text{G}$ in **a** and $125\ \text{G}$ in **b**.

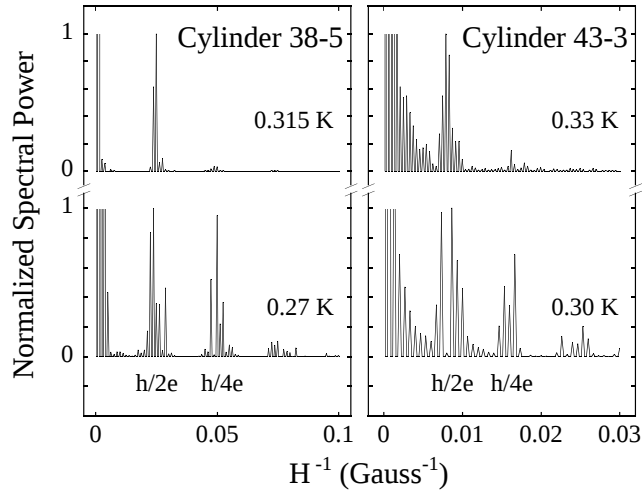


Fig. 3 – Power spectra of selected $R(H)$ data from Figs. 2a and 2b. Each spectrum is normalized to the amplitude of the $h/2e$ peak.

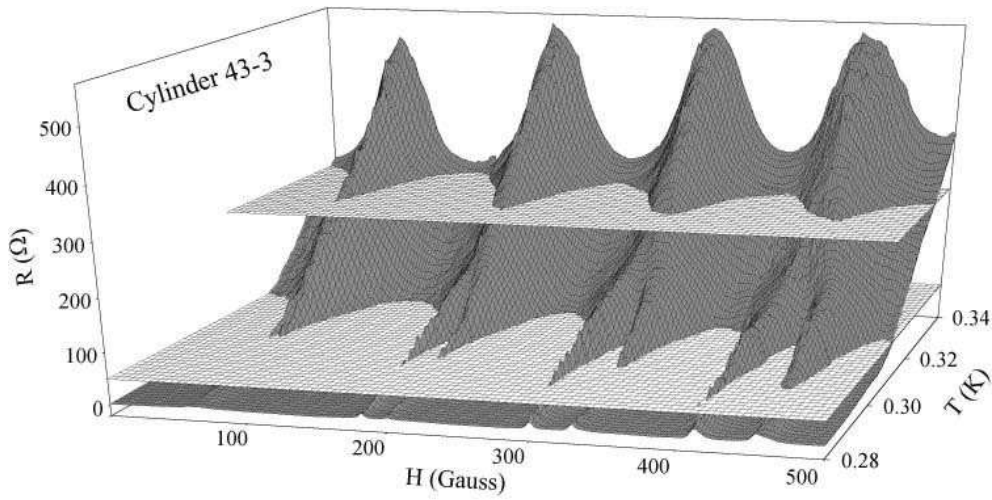


Fig. 4 – Resistance of Cylinder 43-3 plotted as a function of temperature and magnetic field. "Phase boundaries" sliced out by horizontal planes at 50 Ω and 250 Ω are shown (see text).